



Opportunities and Challenges for Hydrotreating of Catalytic Fast Pyrolysis Oil to Fuels

Kristiina Iisa, Xiaolin Chen, Calvin Mukarakate,
Abhijit Dutta, Gina Fioroni, Michael Griffin, Eric Tan

TCSBiomass 2024


September 9-12, 2024

Fuel via Hydrotreating of Catalytic Fast Pyrolysis Oils

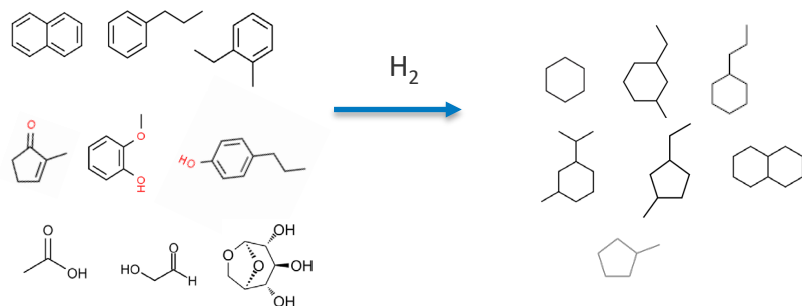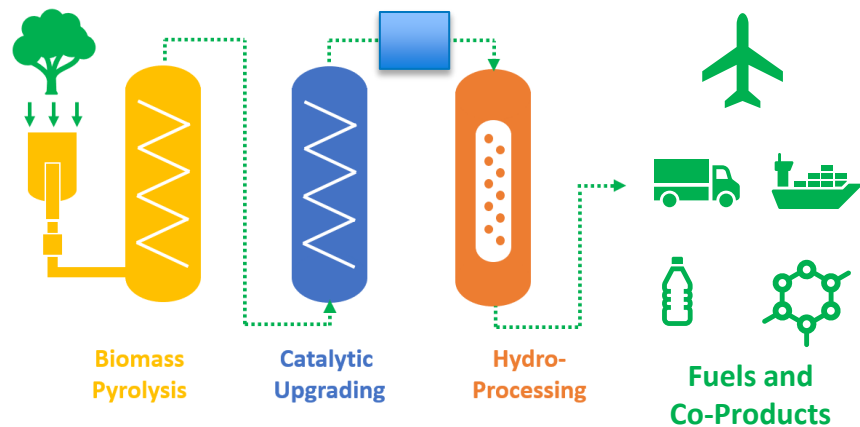

- Fast pyrolysis produces liquid oil at a high yield
- Product has high oxygen content (~30% O dry basis) and is reactive
- Requires several stages of hydrotreating to produce hydrocarbon fuels
- Catalytic fast pyrolysis (CFP)
 - Utilizes vapor phase upgrading over a catalyst to produce a more deoxygenated (15-22% O) and stable oil product
 - Lower concentrations of reactive components
 - CFP oils still require hydroprocessing for final deoxygenation
- A valuable source of **cycloalkanes** that are not easily produced from other biomass sources

Hydrotreating of CFP Oils to Gasoline and Diesel


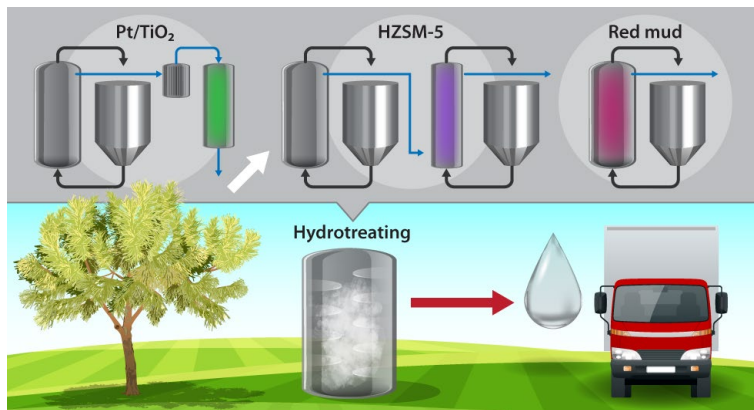


- Three CFP oils produced from pine
- Hydroprocessed under identical conditions
 - NiMo/Al₂O₃, 130 bar, 400°C, LHSV 0.2 h⁻¹
 - Distilled to gasoline and diesel cuts

lisa et al., Energy Fuels, 2023, 37, 19653
<https://doi.org/10.1021/acs.energyfuels.3c03239>

Catalyst	Zeolite HZSM-5	HDO Pt/TiO ₂	Red mud
Mode	Ex situ	Ex situ	In situ
Pyrolysis reactor	Fluidized bed	Fluidized bed	Fluidized bed
Upgrading reactor	Fluidized bed	Fixed bed	-
Pyrolysis temperature, °C	500	500	400
Upgrading temperature, °C	500	400	-
Feed gas	100% N ₂	85% H ₂ /15% N ₂	15% N ₂ /85% recycle gas
Catalyst regeneration	no	yes	no

Hydrotreating of Three CFP Oils

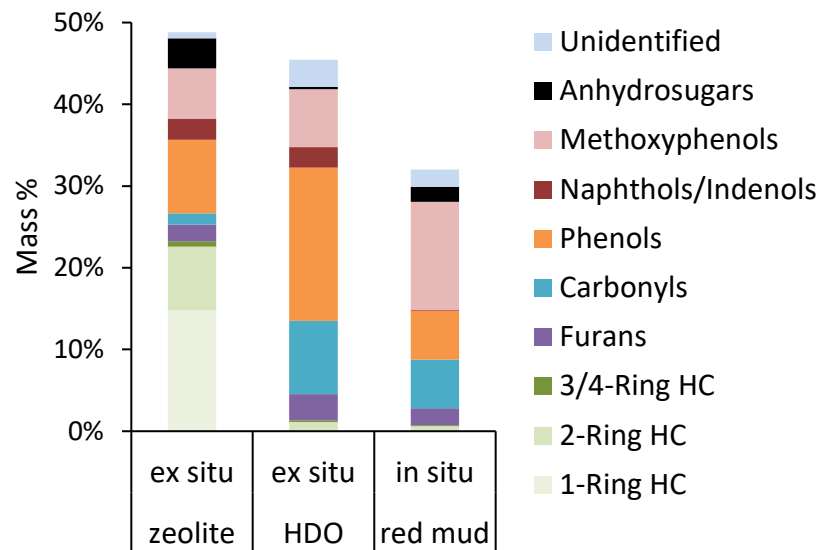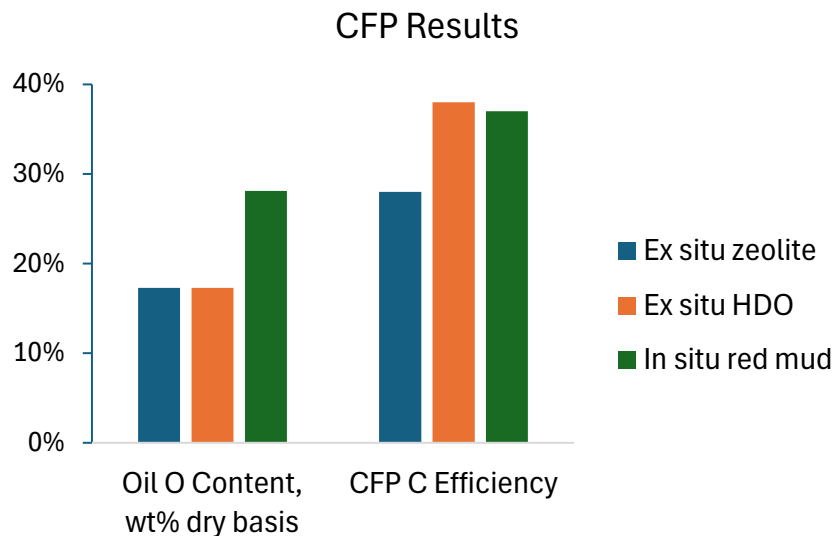


- *Ex situ* zeolite and *ex situ* HDO catalyst produced CFP oils with low oxygen contents: 17 wt% O on dry basis
- *Ex situ* HDO catalyst and *in situ* red mud catalyst gave high carbon yields of CFP oil: 37-38%

- CFP oil compositions varied
 - Zeolite: aromatic hydrocarbons and oxygenates
 - HDO: carbonyls and phenols
 - Red mud: methoxyphenols & other oxygenates


Hydrotreating Results

Hydrotreating Results

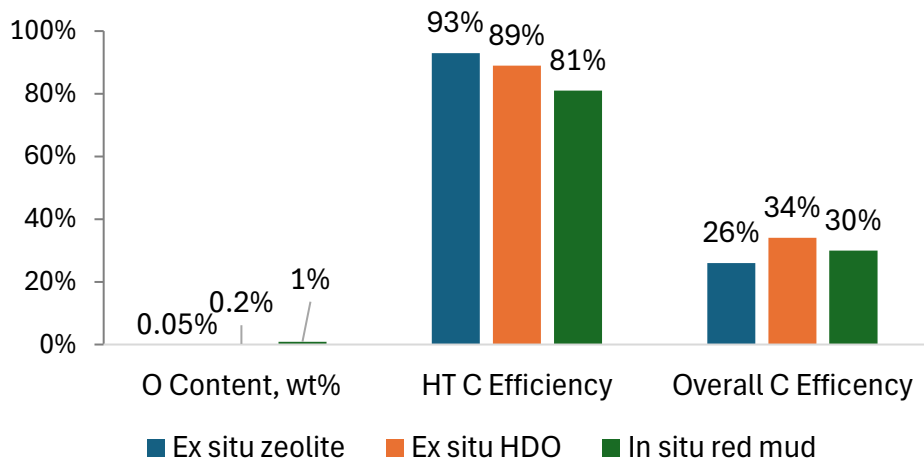

- Low oxygen content in products for ex situ
- High hydrotreating carbon efficiency for ex situ processes
- Overall carbon efficiency from biomass to fuels highest for HDO (Pt/TiO₂) catalyst


GC-MS Analysis

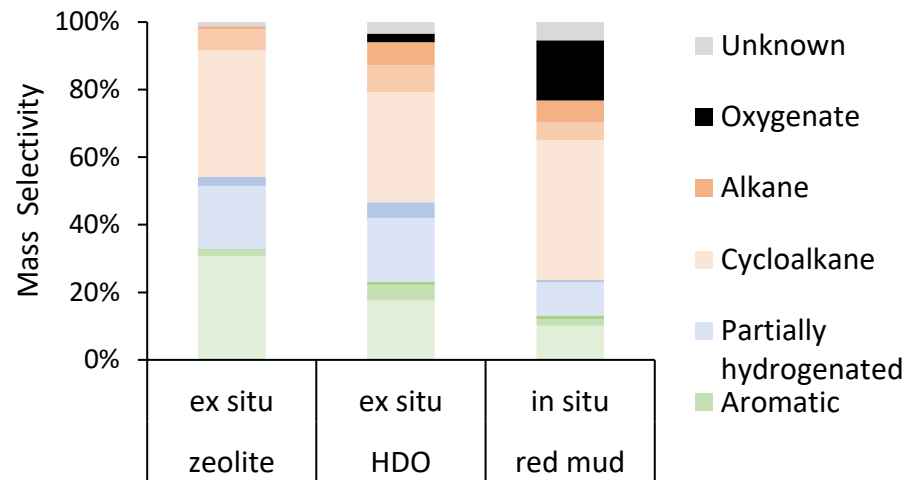

- Fully aromatic hydrocarbons (benzenes, naphthalenes)
- Partially hydrogenated aromatics (e.g. tetralins)
- Cycloalkanes (e.g., cyclohexanes, decanes)
- Oxygenates

Fractionation and Fuel Properties

Distillation Yields

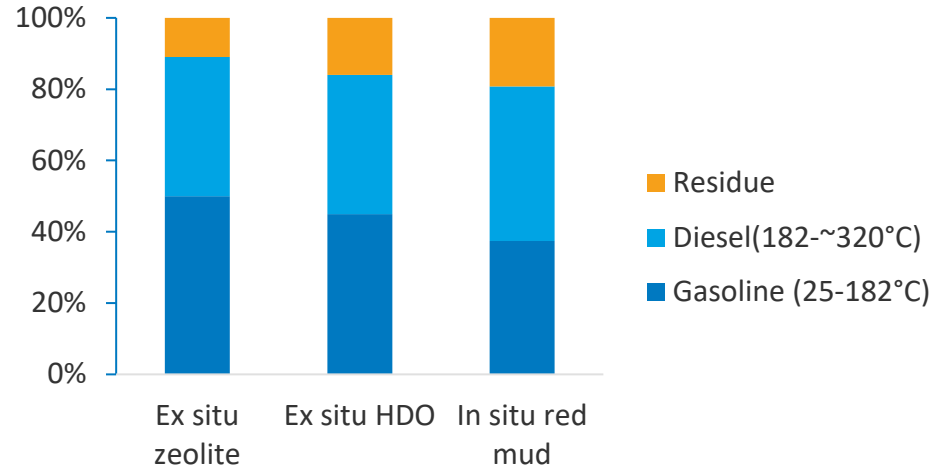


	Riser ex situ CFP	Fixed-bed ex situ CFP	In situ CFP
Gasoline: RON	74	67	59
MON	69	62	55
(RON+MON)/2	71	65	57
Vapor pressure, psi	1.8	2.6	2.8
Diesel: Cetane Number DCN	22	24	26

Diesel with Higher Cetane Number


- Diesel of poor quality
- Hypothesis: add hydrogenation zone prior to hydrotreating

Standalone hydrotreating with

- NiMo/Al₂O₃, 385°C, 125 bar (1800 psi), 0.2 h⁻¹
- Long non-isothermal zone with NiMo/Al₂O₃

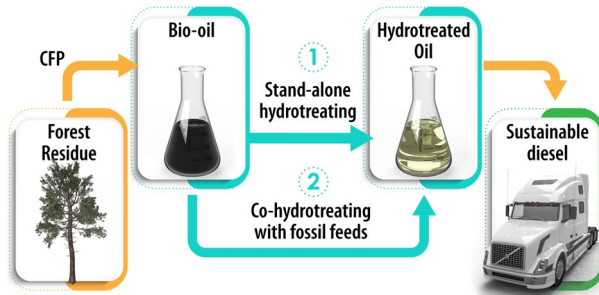

Chen et al., *Energy Adv.*, 2024, 3, 1121
<https://doi.org/10.1039/d4ya00098f>

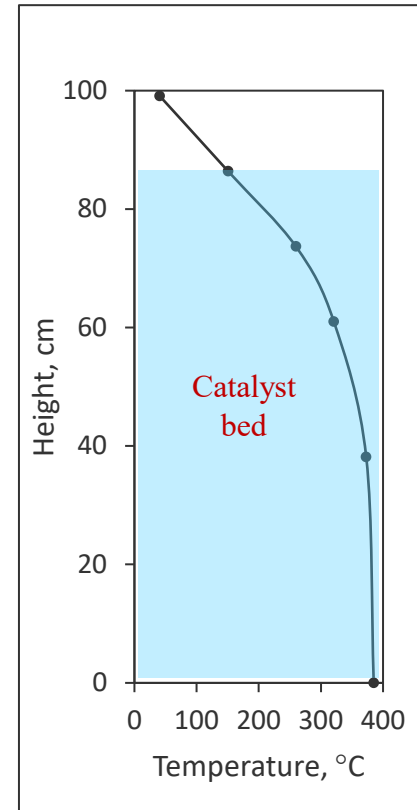

Standalone HT for Diesel


HT Operating Conditions	Previous	Modified
CFP oil O content, wt% db	16%±1%	17%
Product Yield, g/g CFP oil	76%±2%	75%±1%
Product C Yield	89%±2%	89%±1%
O, wt%	0.4%	≤ 0.3%
H:C, mol: mol	1.71	2.01
Density, g/ml	0.851	0.740

Distillation Yields

Gasoline range, wt%	45%	51%
Diesel range, wt%	39%	45%
Residue, wt%	16%	4%

Diesel cetane number	24	45
-----------------------------	-----------	-----------

GC x GC Analysis of Diesel

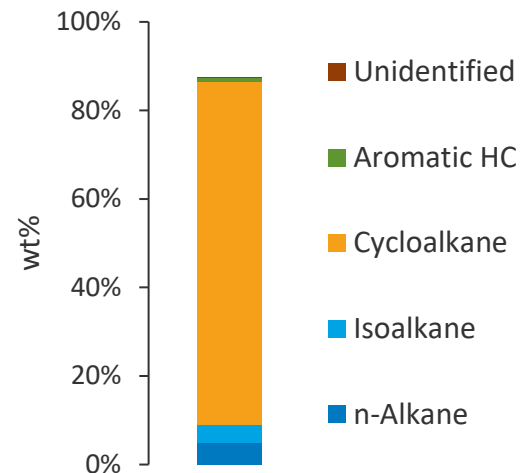


- Adding a long transition zone enhanced hydrogenation and cetane number without negatively impacting product yield
- **78 wt% of products cycloalkanes**

Co-Hydrotreating of CFP Oil to Diesel

- Co-hydrotreating with **straight-run diesel (SRD)**
Hydrotreating conditions milder than typically used for standalone hydrotreating of CFP oil

	Typical SRD HT	Standalone CFP oil HT	Used here
Pressure, bar	40-60	>100	55
Temperature,	320-350	385-400	325
LHSV, h ⁻¹	1-2.5	~0.2	1.0

	CFP oil	SRD
C, wt%	72.6	86.6
H, wt%	7.3	13.2
O, wt%	19.4	≤ 0.3
N, wt%	0.2	0.03
S, wt%	< 0.01	0.2
% Modern carbon	104.1±0.3	< 0.44

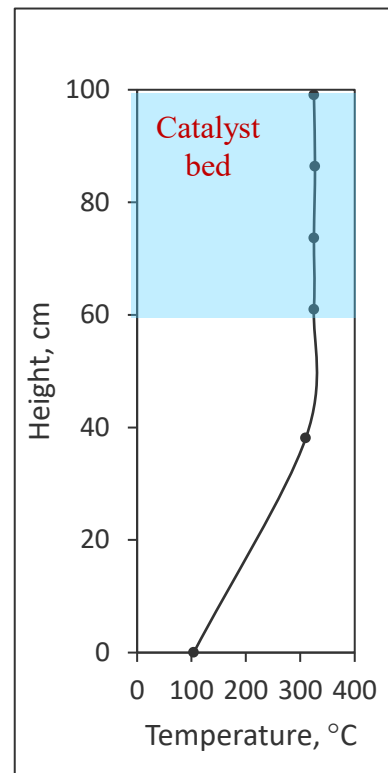

Co-Hydrotreating for Diesel

Catalyst	NiMoS _x /Al ₂ O ₃		CoMoS _x /Al ₂ O ₃	
	SRD	80%SRD/20%CFP	SRD	80%SRD/20%CFP
Feed				
Carbon Efficiency	100	100	101	95
C, wt%	86.34	86.98	87.01	86.77
H, wt%	13.39	13.22	13.48	12.95
O, wt%	≤0.3	≤0.3	≤0.3	≤0.3
N, wt%	0.03	0.04	0.02	0.04
S, wt%	0.01	0.03	0.02	0.04
H:C, mol: mol	1.86	1.82	1.86	1.79
Cetane (ICN)	50	45	48	42
Density, g/mL	0.83	0.83	0.83	0.83
Modern carbon, %	<0.44	19.6±0.1	<0.44	19.0±0.1

- Good deoxygenation was achieved during co-HT despite milder operating conditions
- NiMo gave a higher hydrogenation and cetane number than CoMo did
- C-14 analysis suggested ~95% C incorporation from CFP oil


Hydrotreating for Sustainable Aviation Fuel (SAF)

CFP Catalyst	Pt/TiO ₂	HZSM-5
Catalyst type	Bifunctional HDO (metal- acid)	Zeolite (solid acid)
Upgrading reactor	Fixed bed	Riser
Feed	50% Pine/50% FR	Pine
Gas	85% H ₂	N ₂
Pyrolysis temperature, °C	500	500
Upgrading temperature, °C	400	550
O, wt% daf	16%	18%
H:C, mol/mol	1.22	1.11
H:C _{eff} , mol/mol	0.92	0.75

Hydrotreated in a process similar to that for diesel

- Final temperature 385°C, pressure 125 bar (1800 psi), 0.2 h⁻¹,
- NiMo/Al₂O₃ catalyst

Distilled to fuel cuts


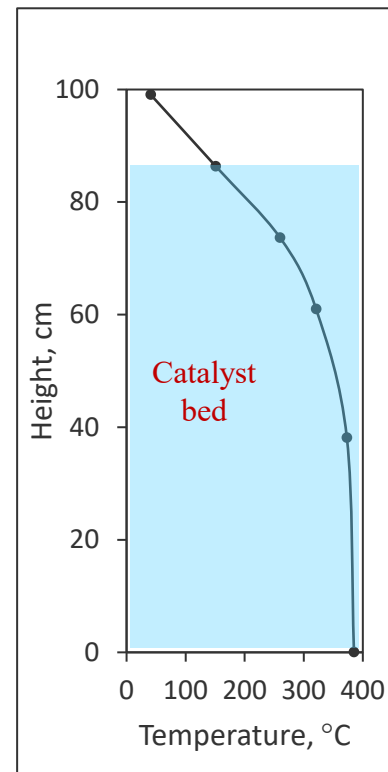


SAF Fraction Properties

	SIMDIS, 10%, °C	SIMDIS, FBP, °C	Flash Point, °C	Freeze Point, °C	Density, g/cm ³	LHV, MJ/kg	C, wt%	H, wt%	N, wt%	O, wt%
ASTM D7566/ D4054	130-160	250-330	>38	max -40	775-840	>42.8	NA	NA	NA	<0.5
ZSM-5	158	281	50	<-70	834	43.0	86.5	13.6	0.0	<0.1
Pt/TiO ₂	158	286	47	<-70	833	43.0	86.5	13.8	0.0	<0.1

- Product distilled to fuel cuts
- Jet-range product met aviation fuel specifications with respect to volatility, flash and freeze points, density, heating value, and oxygen content.

Hydrotreating of CFP Oil to SAF for 400 h

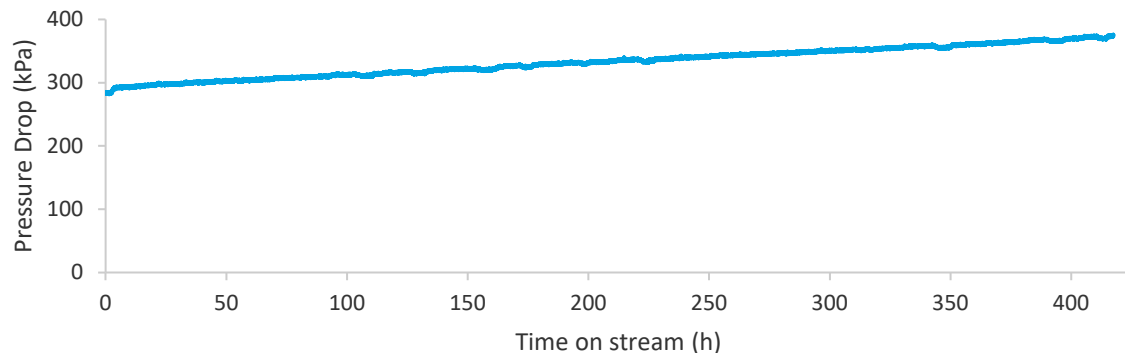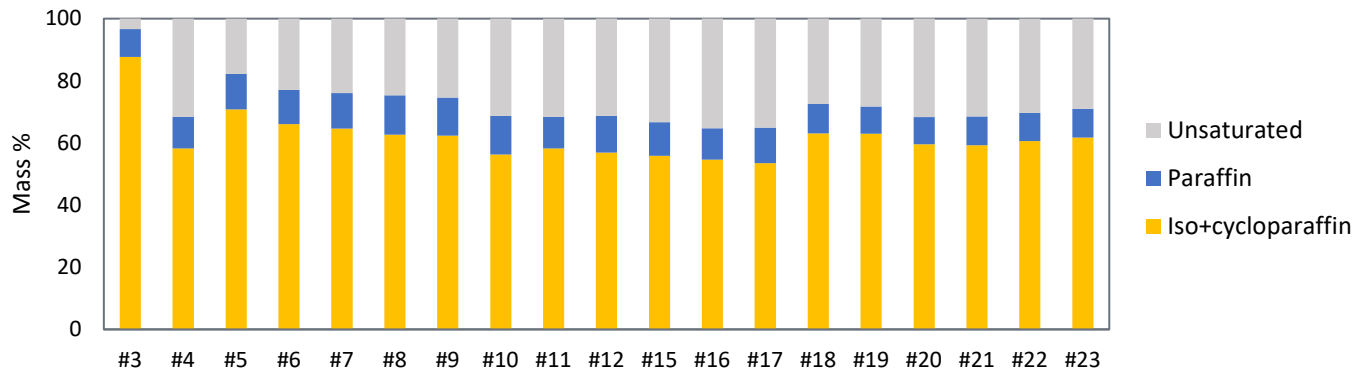


- Completed 400+ hours of hydrotreating for SAF
- O content remained below detection limit (<0.01 wt%)
- Unsaturated (aromatics) slightly increased
- No plugging (pressure drop increased linearly – instrument drift?)

Co-Hydrotreating/cracking CFP Oil to SAF

- Co-hydrotreating/hydrocracking with a mixture of light cycle oil and vacuum gas oil (LCO/VGO)
 - 385°C, NiMoS_x/Al₂O₃, 1 h⁻¹
 - 400°C, NiW/Zeolite, 1 h⁻¹


Jet Fraction Properties	D4054/D7566	LGO/VGO	20%CFP/ 80%LCO/VGO
Flash point, °C	38-66	43	45
Freeze point, °C	≤-40	<-75°C	<-75°C
LHV, MJ/kg	≥42.8	43.4	42.9
Density @ 15°C, kg/m ³	755-884	811	831
Viscosity @-20 °C, mm ² /sK	≤8	3.8	3.9
Surface Tension @ 20°C, mN/m	~26	26.2	27.2

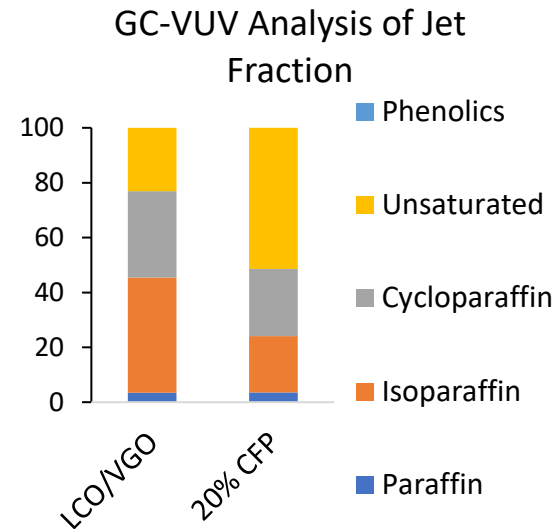

- Co-hydrotreating/hydrocracking with CFP oil increased unsaturated (aromatics and olefins)
- No phenolics or O detected
- Measured jet properties within range

Hydrotreating for Marine Fuel

- Goal to produce marine fuel compatible with very low sulfur fuel oil (VLSFO) and residual marine fuel ISO8217 guidelines
- Complete deoxygenation may not be necessary

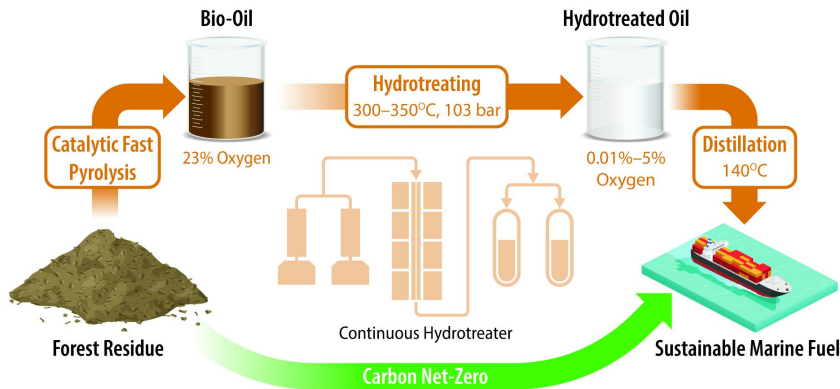

Hydrotreating condition	ISO 8217 RMK 700 grade	300°C, 0.2 g/(gh)
O, wt% daf		5
Density, g/L	≤ 1010	1013
Acid number, mg KOH/g	≤ 2.5	0
H ₂ O, wt%	≤ 0.5	0.07
Flash point, °C	≥ 60	66.7
Spot test with 50 vol% VLSFO	≤ 2	1
Thermal aging, wt%	<0.1	0.01
Chemical aging, wt%	<0.1	0.02

Opportunities and Challenges

- Catalytic fast pyrolysis oil can be upgraded to different fuel cuts
 - Diesel, SAF, marine
 - Via standalone hydrotreating or co-processing with petroleum streams
- Challenges remain
 - Quality of products
 - Additional processing (e.g., hydrogenation)
 - Severe conditions (temperature, pressure, space velocity) required
 - Good deoxygenation for co-processing at milder conditions
 - Catalyst deactivation
 - Hydrogenation activity
 - Deoxygenation activity stable
 - Oil polymerization and plugging problems possible
 - Quality criteria for feeds

Acknowledgments

- US DOE Bioenergy Technologies Office for Funding
- Scott Palmer, Pierce Carson, Kelly Orton, Guy Winters, Cody Wrasman, Tim Panfil, Calvin Mukarakate
- Kelly Orton, Xiaolin Chen, Scott Palmer, Tyler Cary, Sean West, Jim Stunkel, Alex Rein
- Andy Young, Kristen Hampton, Mary Kate Fairley, Mauro Lua, Brenda Yamen, Anastasia Kendl
- Earl Christensen, Liz Ware, Nick Katsiotis, Cheyenne Paeper, Rianna Martinez, Cosette Turvold, Renee Happs, Heidi Pilath
- Stephen Tifft, Nolan Wilson, Caleb Coatney
- Bob McCormick, Gina Fioroni, Jon Luecke, Cameron Hays
- Abhijit Dutta, Mike Talmadge
- Mike Griffin, Calvin Mukarakate, Mark Nimlos, Steven Rowland, Susan Habas, Matt Yung, Fred Baddour
- Huamin Wang, Miki Santosa (PNNL)
- INL for providing feedstocks
- Utah State University for red mud CFP oil
- Johnson Matthey for providing catalysts



Thank you!

www.nrel.gov

This work was authored by the National Renewable Energy Laboratory, operated by Alliance for Sustainable Energy, LLC, for the U.S. Department of Energy (DOE) under Contract No. DE-AC36-08GO28308. Funding provided by U.S. Department of Energy Office of Energy Efficiency and Renewable Energy Bioenergy Technologies Office. The views expressed in the article do not necessarily represent the views of the DOE or the U.S. Government. The U.S. Government retains and the publisher, by accepting the article for publication, acknowledges that the U.S. Government retains a nonexclusive, paid-up, irrevocable, worldwide license to publish or reproduce the published form of this work, or allow others to do so, for U.S. Government purposes.

